



**EARLE M. JORGENSEN
COMPANY**

REFERENCE BOOK

**ALLOY • ALUMINUM • BRASS • BRONZE
CARBON • CAST IRON • CHROME • NICKEL
STAINLESS • SUPER ALLOY • TITANIUM
BAR • PIPE • PLATE • SHEET • TUBE**

www.emjmetals.com

A

SECTION A

COLD FINISHED CARBON BARS

and

COLD ROLLED STRIP

1008/1010 COLD ROLLED STRIP	2
1018	3-8
Rounds, Hexagons, Squares, Flats	
1040/42/45	9-10
Rounds, Hexagons, Squares	
1045 PRECISION SHAFTING	11-12
1213 and 1215 (Screw Machine Stock)	13-14
Hexagons, Rounds, Squares	
12L14 SUPER FREE MACHINING — LEADED	15-16
Rounds, Hexagons, Squares	
1117 and 11L17 (Leaded)	17-19
Squares, Rounds, Hexagons, Flats	
1137 and 1141	20-21
Rounds	
STRESSPROOF® and 1144 HI STRESS	22-23
Hexagons, Cold Drawn Rounds, Ground & Polished Rounds	
FATIGUE-PROOF®	24
Cold Drawn Rounds	
1045/1050/1045 Microalloy CHROME PLATED - ROUNDS	25
1050 CARBON BAR FOR TIE-ROD APPLICATION	26
Rounds	

COLD ROLLED STRIP — 1008/1010

UNS G10080 UNS G10100

Temper: Number 2 (Half-Hard)

Finish: Number 2 (Regular Bright)

Edge: 3" and narrower—No. 4 (Round)

Over 3" wide—No. 3 (Square)

Color Marking: Ends painted Blue

This grade is a flat cold rolled carbon steel, processed to give such useful characteristics as dimensional accuracy and improved surface, along with desired mechanical properties. Half-hard, or No. 2 temper, is a moderately stiff product intended for limited bending. It may be bent 90° across the direction of rolling around a radius equal to the thickness.

ANALYSIS

Carbon	Manganese	Phosphorus	Sulphur
.08/.13	.30/.60	.04 Max.	.05 Max.

APPLICATIONS — This grade of Cold Rolled Strip is suitable for many general applications where dimensional accuracy and stiffness are required. Bending and forming may be performed to a limited degree.

MECHANICAL PROPERTIES — The following values are average and may be considered as representative of the grade but are not generally reported:

Tensile Strength (psi)	Rockwell Hardness B Scale
60,000/78,000	70/85

WELDABILITY — This grade is easily welded by all the welding processes, and the resultant welds and joints are of extremely high quality. The grade of welding rod to be used depends on the thickness of section, design, service requirements, etc.

COLD ROLLED STRIP



Stock Lengths 12'

Thickness In Inches	Estimated Weight, Lbs.		Thickness In Inches	Estimated Weight, Lbs.	
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar
$1/16$ x			$3/32$ x		
$1/4$.0532	.6381	2	.6381	7.657
$3/8$.0798	.9572	$2 1/2$.7976	9.572
$1/2$.1064	1.276	3	.9572	11.49
$5/8$.1329	1.595	4	1.276	15.31
$3/4$.1595	1.914	$1/8$ x		
$7/8$.1861	2.233	$3/16$.0798	.9572
1	.2127	2.552	$1/4$.1064	1.276
$1 1/8$.2393	2.871	$3/8$.1595	1.914
$1 1/4$.2659	3.191	$1/2$.2127	2.552
$1 1/2$.3191	3.829	$5/8$.2659	3.191
$1 3/4$.3722	4.467	$3/4$.3191	3.829
2	.4254	5.105	$7/8$.3722	4.467
$2 1/2$.5318	6.381	1	.4254	5.105
3	.6381	7.657	$1 1/8$.4786	5.743
$3/32$ x			$1 1/4$.5318	6.381
$3/8$.1196	1.436	$1 1/2$.6381	7.657
$1/2$.1595	1.914	$1 3/4$.7445	8.933
$5/8$.1994	2.393	2	.8508	10.21
$3/4$.2393	2.871	$2 1/2$	1.064	12.76
$7/8$.2792	3.350	3	1.276	15.31
1	.3191	3.829	4	1.702	20.42
$1 1/8$.3589	4.307	$4 1/2$	1.914	22.97
$1 1/4$.3988	4.786	5	2.127	25.52
$1 1/2$.4786	5.743	6	2.552	30.63
$1 3/4$.5583	6.700			

1018 COLD FINISHED BARS

ASTM A 108 UNS G10180

Color Marking: Ends painted Black

A low-carbon steel, having higher manganese content than certain other low-carbon steels, such as 1020. Being richer in manganese, 1018 is a better steel for carburized parts, since it produces a harder and more uniform case. It also has higher mechanical properties and better machining characteristics. The hot rolled bars used in the manufacture of this product are of special quality.

Most cold finished bars are produced by cold drawing. In this process, oversize hot rolled bars, which have been cleaned to remove scale, are drawn through dies to the required size. The larger sizes are generally turned and polished, the hot rolled bars having been machine turned, rather than drawn, followed by abrasive polishing. Turned and polished bars tend to have a somewhat brighter finish than cold drawn bars.

A greater degree of dimensional accuracy and straightness in round bars is obtained by grinding and polishing. The product resulting from this process is known as Precision Shafting. For description and listing of stock sizes of PRECISION SHAFTING, refer to Pages 11 and 12 of this section.

ANALYSIS

Carbon	Manganese	Phosphorus	Sulphur
.15/.20	.60/.90	.04 Max.	.05 Max.

APPLICATIONS — Suitable for parts requiring cold forming, such as crimping, swaging or bending. However, for severe bends, stress relieving may be necessary to prevent cracking. Especially suitable for carburized parts requiring soft core and high surface hardness, such as gears, pinions, worms, king pins, chain pins, ratchets, dogs, etc.

MECHANICAL PROPERTIES — The following values are average and may be considered as representative of the grade:

	Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
1" rd., cold drawn	85,000	70,000	28%	55%	167
7" rd., turned & polished	70,000	45,000	36%	58%	143

MACHINABILITY— 1018 has a machinability rating of 78%, based on 1212 as 100%. Average surface cutting speed is 130 feet per minute.

WELDABILITY — This grade is easily welded by all the welding processes, and the resultant welds and joints are of extremely high quality. The grade of welding rod to be used depends on the thickness of section, design, service requirements, etc.

HARDENING — This grade will respond to any of the standard carburizing methods and subsequent heat treatments. For a hard case and tough core, the following heat treatment is suggested: Carburize at 1650°-1700°F for approximately eight hours, cool in box and reheat to 1400°-1450°F. Quench in water and draw at 300°-350°F.

1018 COLD FINISHED BARS (Continued)



1018 COLD FINISHED ROUNDS

Stock Lengths: 12' and 20' Approx.

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.	
	Per Foot	20-Ft. Bar		Per Foot	20-Ft. Bar		Per Foot	20-Ft. Bar
1/8	.0418	.8353	1 15/16	10.03	200.7	4 3/8	51.16	1023
5/32	.0653	1.305		2	10.69	213.8	7/16	52.63
3/16	.0940	1.879	1/16		11.37	227.4	1/2	54.13
7/32	.1279	2.558	1/8	12.07	241.4	9/16	55.64	1113
1/4	.1671	3.341	3/16	12.79	255.8	5/8	57.18	1143
9/32	.2114	4.229	1/4	13.53	270.6	11/16	58.73	1175
5/16	.2610	5.220	5/6	14.29	285.9	3/4	60.31	1206
11/32	.3158	6.317	3/8	15.08	301.5	7/8	63.52	1270
3/8	.3759	7.517	7/16	15.88	317.6	15/16	65.16	1303
13/32	.4411	8.822	1/2	16.71	334.1	5	66.82	1336
7/16	.5116	10.23	9/16	17.55	351.0		1/8	70.21
15/32	.5873	11.75	5/8	18.42	368.4	1/4	73.67	1473
1/2	.6682	13.26	11/16	19.31	386.1	5/16	75.44	1509
17/32	.7544	15.09	3/4	20.21	404.3	3/8	77.22	1544
9/16	.8457	16.91	13/16	21.14	422.9	7/16	79.03	1581
19/32	.9425	18.85	7/8	22.09	441.9	1/2	80.86	1617
5/8	1.044	20.88	15/16	23.06	461.3	5/8	84.57	1691
11/16	1.263	25.27	3	24.06	481.1	3/4	88.37	1767
23/32	1.381	27.62		1/16	25.07	501.4	7/8	92.26
3/4	1.504	30.07	1/8	26.10	522.0	15/16	94.23	1885
49/64	1.567	31.34	3/16	27.16	543.1	6	96.22	1924
13/16	1.765	35.29	1/4	28.23	564.6		1/8	100.3
7/8	2.046	40.93	5/16	29.33	586.6	1/4	104.4	2088
15/16	2.349	46.98	3/8	30.45	608.9	3/8	108.6	2172
I	2.673	53.46	7/16	31.58	631.7	1/2	112.9	2259
	1/64	2.757	1/2	32.74	654.8	3/4	121.8	2436
1/32	2.843	56.85	9/16	33.92	678.4	7	131.0	2619
1/16	3.017	60.35	5/8	35.12	702.5		1/4	140.5
1/8	3.383	67.66	11/16	36.35	726.9	1/2	150.4	3007
3/16	3.769	75.38	3/4	37.59	751.7	3/4	160.5	3211
1/4	4.176	83.53	7/8	40.14	802.7	8	171.1	3421
5/16	4.604	92.09	15/16	41.44	828.8		1/2	193.1
3/8	5.053	101.1	4	42.77	855.3	9	216.5	4330
7/16	5.523	110.5		1/8	45.48		909.6	1/2
1/2	6.014	120.3	3/16	46.87	937.4	10	267.3	5346
9/16	6.526	130.5	1/4	48.28	965.6		1/2	294.7
5/8	7.058	141.2	5/16	49.71	994.2	11	323.4	6468
11/16	7.612	152.2	12				1/2	353.5
3/4	8.186	163.7						
13/16	8.781	175.6						
7/8	9.397	187.9						

1018 COLD FINISHED BARS (Continued)



1018 COLD DRAWN HEXAGONS

Stock Lengths 10' to 12'

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar	
3/16	.1036	1.243	1	2.947	35.37	2	11.79	141.5	
1/4	.1842	2.210		1/16	3.327	39.93	1/8	13.31	159.7
5/16	.2878	3.454		1/8	3.730	44.76	1/4	14.92	179.0
3/8	.4145	4.973		3/16	4.156	49.87	3/8	16.62	199.5
7/16	.5641	6.769		1/4	4.605	55.26	7/16	17.51	210.1
1/2	.7368	8.842		5/16	5.077	60.93	1/2	18.42	221.0
9/16	.9325	11.19		3/8	5.572	66.87	5/8	20.31	243.7
5/8	1.151	13.82		7/16	6.090	73.08	3/4	22.29	267.5
11/16	1.393	16.72		1/2	6.631	79.56	3	26.53	318.3
3/4	1.658	19.89		9/16	7.196	86.35	1/8	28.78	345.4
7/8	2.257	27.08		5/8	7.783	93.39	1/4	31.13	373.6
15/16	2.590	31.08		3/4	9.026	108.3	1/2	36.10	433.2
				13/16	9.682	116.2	3/4	41.45	497.3
				7/8	10.36	124.3	4	47.16	565.9



1018 COLD FINISHED SQUARES

KEY STOCK
Stock Lengths 12'

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar	
1/8	.0531	.6381	1	3.403	40.84	2 1/4	17.23	206.7	
3/16	.1196	1.436		1/16	3.842	46.10	3/8	19.20	230.4
1/4	.2127	2.552		1/8	4.307	51.69	1/2	21.27	255.2
5/16	.3323	3.988		3/16	4.799	57.59	5/8	23.45	281.4
3/8	.4786	5.743		1/4	5.318	63.81	3/4	25.74	308.8
7/16	.6514	7.817		5/16	5.863	70.35	3	30.63	367.5
1/2	.8508	10.21		3/8	6.434	77.21	1/4	35.95	431.4
9/16	1.077	12.92		7/16	7.032	84.39	1/2	41.69	500.3
5/8	1.329	15.95		1/2	7.657	91.89	3/4	47.86	574.3
11/16	1.609	19.30		9/16	8.309	99.71	4	54.45	653.4
3/4	1.914	22.97		5/8	8.987	107.8	1/2	68.91	827.0
13/16	2.247	26.96		3/4	10.42	125.1	5	85.08	1021
7/8	2.606	31.27		7/8	11.96	143.6	1/2	102.9	1235
15/16	2.991	35.89		2	13.61	163.4	6	122.5	1470
				1/8	15.37	184.4			

1018 COLD FINISHED BARS (Continued)



1018 COLD DRAWN FLATS

Stock Lengths 10' and 12'

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.	
	Per Foot	20-Ft. Bar		Per Foot	20-Ft. Bar		Per Foot	20-Ft. Bar
1/8 x			3/16 x			5/16 x		
3/16	.0798	.9576	8	5.105	61.26	1 1/2	1.595	19.14
1/4	.1064	1.276	9	5.743	68.91	1 5/8	1.729	20.74
5/16	.1329	1.595	10	6.381	76.57	1 3/4	1.861	22.33
3/8	.1595	1.914	12	7.657	91.89	2	2.127	25.52
7/16	.1861	2.233	1/4 x			2 1/4	2.393	28.71
1/2	.2127	2.552		5/16	.2659	3.191	2 1/2	2.659
9/16	.2393	2.872	3/8	.3191	3.829	2 3/4	2.925	35.10
5/8	.2659	3.191	7/16	.3722	4.467	3	3.191	38.29
11/16	.2925	3.510	1/2	.4254	5.105	3 1/2	3.722	44.68
3/4	.3191	3.829	9/16	.4786	5.743	4	4.254	51.05
7/8	.3722	4.467	5/8	.5318	6.381	4 1/2	4.786	57.43
1	.4254	5.105	3/4	.6381	7.657	5	5.318	63.81
1 1/8	.4786	5.743	7/8	.7445	8.933	5 1/2	5.849	70.19
1 1/4	.5318	6.381	1	.8508	10.21	6	6.381	76.57
1 3/8	.5849	7.019	1 1/8	.9572	11.49	8	8.508	102.1
1 1/2	.6381	7.657	1 1/4	1.064	12.76	10	10.64	127.6
1 3/4	.7445	8.933	1 3/8	1.170	14.04	12	12.76	153.1
2	.8508	10.21	1 1/2	1.276	15.31	3/8 x		
2 1/4	.9572	11.49	1 5/8	1.383	16.59		7/16	.5583
2 1/2	1.064	12.76	1 3/4	1.489	17.87	1/2	.6381	7.657
2 3/4	1.170	14.04	1 7/8	1.595	19.14	9/16	.7179	8.615
3	1.276	15.31	2	1.702	20.42	5/8	.7976	9.572
3 1/2	1.489	17.87	2 1/4	1.914	22.97	3/4	.9572	11.49
4	1.702	20.42	2 1/2	2.127	25.52	7/8	1.117	13.40
4 1/2	1.914	22.97	2 3/4	2.340	28.08	1	1.276	15.31
5	2.127	25.52	3	2.552	30.63	1 1/8	1.436	17.23
6	2.552	30.63	3 1/4	2.765	33.18	1 1/4	1.595	19.14
8	3.403	40.84	3 1/2	2.978	35.73	1 3/8	1.755	21.06
10	4.254	51.05	3 3/4	3.191	38.29	1 1/2	1.914	22.97
12	5.105	61.26	4	3.403	40.84	1 5/8	2.074	24.89
3/16 x			4 1/4	3.616	43.39	1 3/4	2.233	26.80
1/4	.1595	1.914	4 1/2	3.829	45.94	1 7/8	2.393	28.72
5/16	.1994	2.393	4 3/4	4.041	48.50	2	2.552	30.63
3/8	.2393	2.871	5	4.254	51.05	2 1/4	2.871	34.46
7/16	.2792	3.350	5 1/4	4.467	53.60	2 1/2	3.191	38.29
1/2	.3191	3.829	5 1/2	4.679	56.15	2 3/4	3.510	42.11
5/8	.3988	4.786	5 3/4	4.892	58.70	3	3.829	45.94
3/4	.4786	5.743	6	5.105	61.26	3 1/4	4.148	49.77
7/8	.5583	6.700	6 1/2	5.530	66.36	3 1/2	4.467	53.60
1	.6381	7.657	7	5.956	71.47	3 3/4	4.786	57.43
1 1/8	.7179	8.614	8	6.806	81.68	4	5.105	61.26
1 1/4	.7976	9.572	9	7.657	91.89	4 1/4	5.424	65.09
1 3/8	.8774	10.53	10	8.508	102.1	4 1/2	5.743	68.91
1 1/2	.9572	11.49	11	9.359	112.3	4 3/4	6.062	72.74
1 3/4	1.117	13.40	12	10.21	122.5	5	6.381	76.57
1 7/8	1.196	14.35	14 5/8	12.44	149.3	5 1/4	6.700	80.40
2	1.276	15.31	5/16 x			5 1/2	7.019	84.23
2 1/4	1.436	17.23		3/8	.3988	4.786	5 3/4	7.338
2 1/2	1.595	19.14	7/16	.4653	5.583	6	7.657	91.89
2 3/4	1.755	21.06	1/2	.5318	6.381	6 1/2	8.295	99.54
3	1.914	22.97	9/16	.5982	7.179	7	8.933	107.2
3 1/4	2.074	24.89	5/8	.6647	7.976	8	10.21	122.5
3 1/2	2.233	26.80	3/4	.7976	9.572	9	11.49	137.8
3 3/4	2.393	28.71	7/8	.9306	11.17	10	12.76	153.1
4	2.552	30.63	1	1.064	12.76	11	14.04	168.5
4 1/2	2.871	34.46	1 1/8	1.196	14.36	12	15.31	183.8
5	3.191	38.29	1 1/4	1.329	15.95	13 1/2	17.23	206.7
6	3.829	45.94	1 3/8	1.462	17.55	14 5/8	18.66	224.0

1018 COLD FINISHED BARS (Continued)



1018 COLD DRAWN FLATS (Continued)

Stock Lengths 10' and 12'

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.	
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar
7/16 x			9/16 x			3/4 x		
1/2	.7445	8.933	5/8	1.196	14.35	2 3/4	7.019	84.23
5/8	.9306	11.17	3/4	1.436	17.23	3	7.657	91.89
3/4	1.117	13.40	7/8	1.675	20.10	3 1/4	8.295	99.54
7/8	1.303	15.63	1	1.914	22.97	3 1/2	8.933	107.2
1	1.489	17.87	1 1/4	2.393	28.72	3 3/4	9.572	114.9
1 1/8	1.675	20.10	1 1/2	2.871	34.46	4	10.21	122.5
1 1/4	1.861	22.33	1 3/4	3.350	40.20	4 1/4	10.85	130.2
1 1/2	2.233	26.80	2	3.829	45.95	4 1/2	11.49	137.8
1 3/4	2.606	31.27	2 1/2	4.786	57.43	4 3/4	12.12	145.4
2	2.978	35.73	5/8 x			5	12.76	153.1
2 1/4	3.350	40.20	9/16	1.462	17.54	5 1/2	14.04	168.5
2 1/2	3.722	44.67	3/4	1.595	19.14	6	15.31	183.8
2 3/4	4.094	49.13	7/8	1.861	22.33	6 1/2	16.59	199.1
3	4.467	53.60	1	2.127	25.52	7	17.87	214.4
4	5.956	71.47	1 1/8	2.393	28.71	8	20.42	245.0
4 1/2	6.700	80.40	1 1/4	2.659	31.91	9	22.97	275.7
5	7.445	89.33	1 3/8	2.925	35.10	10	25.52	306.3
6	8.933	107.2	1 1/2	3.191	38.29	11	28.08	337.0
1/2 x			1 5/8	3.456	41.48	12	30.63	367.5
9/16	.9572	11.49	1 3/4	3.722	44.67	14	35.73	428.8
5/8	1.064	12.76	2	4.254	51.05	14 5/8	37.33	448.0
3/4	1.276	15.31	2 1/4	4.786	57.43	7/8 x		
7/8	1.489	17.87	2 1/2	5.318	63.81	1	2.978	35.73
1	1.702	20.42	2 3/4	5.849	70.19	1 1/8	3.350	40.20
1 1/8	1.914	22.97	3	6.381	76.57	1 1/4	3.722	44.67
1 1/4	2.127	25.52	3 1/4	6.913	82.95	1 3/8	4.094	49.13
1 3/8	2.340	28.08	3 1/2	7.445	89.33	1 1/2	4.467	53.60
1 1/2	2.552	30.63	4	8.508	102.1	1 3/4	5.211	62.53
1 5/8	2.765	33.18	4 1/4	9.040	108.5	2	5.956	71.47
1 3/4	2.978	35.73	4 1/2	9.572	114.9	2 1/4	6.700	80.40
2	3.403	40.84	4 3/4	10.10	121.2	2 1/2	7.445	89.33
2 1/4	3.829	45.94	5	10.64	127.6	2 3/4	8.189	98.27
2 1/2	4.254	51.05	5 1/2	11.70	140.4	3	8.933	107.2
2 3/4	4.679	56.15	6	12.76	153.1	3 1/2	10.42	125.1
3	5.105	61.26	6 1/2	13.83	166.0	4	11.91	142.9
3 1/4	5.530	66.36	7	14.89	178.7	4 1/2	13.40	160.8
3 1/2	5.956	71.47	8	17.02	204.2	5	14.89	178.7
3 3/4	6.381	76.57	9	19.14	229.7	5 1/2	16.38	196.6
4	6.806	81.68	10	21.27	255.2	6	17.87	214.4
4 1/4	7.232	86.78	11	23.40	280.8	8	23.82	285.9
4 1/2	7.657	91.89	12	25.52	306.3	10	29.78	357.3
4 3/4	8.083	96.99	14	29.78	357.4	11	32.76	393.1
5	8.508	102.1	14 5/8	31.11	373.3	12	35.73	428.8
5 1/4	8.933	107.2	1 1/16 x			1 x		
5 1/2	9.359	112.3	3/4	1.755	21.06	1 1/8	3.829	45.94
5 3/4	9.784	117.4	1	2.340	28.08	1 1/4	4.254	51.05
6	10.21	122.5	3/4 x			1 3/8	4.679	56.15
6 1/2	11.06	132.7	7/8	2.233	26.80	1 1/2	5.105	61.26
7	11.91	142.9	1	2.552	30.63	1 5/8	5.530	66.36
8	13.61	163.4	1 1/8	2.871	34.46	1 3/4	5.956	71.47
9	15.31	183.8	1 1/4	3.191	38.29	2	6.806	81.68
10	17.02	204.2	1 3/8	3.510	42.11	2 1/4	7.657	91.89
11	18.72	224.6	1 1/2	3.829	45.94	2 1/2	8.508	102.1
12	20.42	245.0	1 5/8	4.148	49.77	2 3/4	9.359	112.3
14	23.82	285.8	1 3/4	4.467	53.60	3	10.21	122.5
14 5/8	24.89	298.7	2	5.105	61.26	3 1/4	11.06	132.7
			2 1/4	5.743	68.91	3 1/2	11.91	142.9
			2 1/2	6.381	76.57	3 3/4	12.76	153.1

1018 COLD FINISHED BARS (Continued)



1018 COLD DRAWN FLATS (Continued)

Stock Lengths 10' and 12'

Size			Size			Size			Size		
In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.
Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar
1 x			1 1/4 x			1 3/4 x			2 1/2 x		
4	13.61	163.4	6	25.52	306.3	5 1/2	32.76	393.1	8	68.06	816.8
4 1/4	14.46	173.5	7	29.78	357.3	6	35.73	428.8	9	76.57	918.9
4 1/2	15.31	183.8	8	34.03	408.4	8	47.64	571.7	10	85.08	1021
4 3/4	16.17	194.0	9	38.29	459.4	10	59.56	714.7	11	93.59	1123
5	17.02	204.2	10	42.54	510.5	11	65.51	786.1	12	102.1	1225
5 1/2	18.72	224.6	11	46.79	561.5	12	71.47	857.6	3 x		
6	20.42	245.0	12	51.05	612.6	2 x			3 1/2	35.73	428.8
6 1/2	22.12	265.4	14	59.56	714.6	2 1/4	15.31	183.8	4	40.84	490.1
7	23.82	285.9	14 5/8	62.21	746.5	2 1/2	17.02	204.2	4 1/2	45.94	551.3
8	27.23	326.7	1 3/8 x			2 3/4	18.72	224.6	5	51.05	612.6
9	30.63	367.5	1 1/2	7.019	84.23	3	20.42	245.0	6	61.26	735.1
10	34.03	408.4	2	9.359	112.3	3 1/4	22.12	265.4	7	71.47	857.6
11	37.44	449.3	3	14.04	168.5	3 1/2	23.82	285.9	8	81.68	980.1
12	40.84	490.1	1 1/2 x			3 3/4	25.52	306.2	10	102.1	1225
14	47.64	571.7	1 5/8	8.295	99.54	4	27.23	326.7	12	122.5	1470
14 5/8	49.77	597.3	1 3/4	8.933	107.2	4 1/2	30.63	367.5	3 1/2 x		
1 1/8 x			2	10.21	122.5	5	34.03	408.4	4	47.64	571.7
1 1/4	4.786	57.43	2 1/4	11.49	137.9	5 1/2	37.44	449.2	4 1/2	53.60	643.2
1 3/8	5.264	63.17	2 1/2	12.76	153.1	6	40.84	490.1	5	59.56	714.7
1 1/2	5.743	68.91	2 3/4	14.04	168.5	7	47.64	571.7	6	71.47	857.6
1 5/8	6.221	74.65	3	15.31	183.8	8	54.45	653.4	7	83.38	1001
1 3/4	6.700	80.40	3 1/4	16.59	199.1	9	61.26	735.1	8	95.29	1143
2	7.657	91.89	3 1/2	17.87	214.4	10	68.06	816.8	9	107.2	1286
2 1/4	8.614	103.4	4	200.42	245.0	11	74.87	898.4	10	119.1	1429
2 1/2	9.572	114.9	4 1/2	22.97	275.7	12	81.68	980.1	12	142.9	1715
3	11.49	137.8	5	25.52	306.3	2 1/4 x			4 x		
4	15.31	183.8	5 1/2	28.08	336.9	2 1/2	19.14	229.7	4 1/2	61.26	735.1
5	19.14	229.7	6	30.63	367.5	2 3/4	21.06	252.7	5	68.06	816.8
6	22.97	275.7	7	35.73	428.8	3	22.97	275.7	6	81.68	980.1
1 1/4 x			8	40.84	490.1	3 1/2	26.80	321.6	6 1/2	88.48	1062
1 3/8	5.849	70.19	9	45.94	551.3	4	30.63	367.5	7	95.29	1143
1 1/2	6.381	76.57	10	51.05	612.6	4 1/2	34.46	413.5	8	108.9	1307
1 5/8	6.913	82.96	11	56.15	673.8	5	38.29	459.4	10	136.1	1634
1 3/4	7.445	89.33	12	61.26	735.1	5 1/2	42.11	505.4	12	163.4	1960
1 7/8	7.976	95.71	14	71.47	857.6	6	45.94	551.3	4 1/2 x		
2	8.508	102.1	1 5/8 x			8	61.26	735.1	5	76.57	918.9
2 1/4	9.572	114.9	2	11.06	132.7	10	76.57	918.9	5 1/2	84.23	1011
2 1/2	10.64	127.6	3	16.59	199.1	2 1/2 x			6	91.89	1103
2 3/4	11.70	140.4	1 3/4 x			2 3/4	23.40	280.8	5 x		
3	12.76	153.1	2	11.91	142.9	3	25.52	306.3	6	102.1	1225
3 1/4	13.83	166.0	2 1/4	13.40	160.8	3 1/2	29.78	357.3	7	119.1	1429
3 1/2	14.89	178.7	2 1/2	14.89	178.7	4	34.03	408.4	8	136.1	1633
3 3/4	15.95	191.4	2 3/4	16.38	196.5	4 1/2	38.29	459.4	10	170.2	2042
4	17.02	204.2	3	17.87	214.4	5	42.54	510.5	6 x		
4 1/2	19.14	229.7	3 1/2	20.84	250.1	5 1/2	46.79	561.5	8	163.4	1961
5	21.27	255.2	4	23.82	285.9	6	51.05	612.6	10	204.2	2450
5 1/2	23.40	280.8	4 1/2	26.80	321.6	7	59.56	714.7	12	245.0	2940
			5	29.78	357.3						

1040/42/45 COLD FINISHED BARS

ASTM A 108 UNS G10400 G10420 G10450

Color Marking: Ends painted Red

This is medium-carbon steel. The higher carbon content imparts higher strength properties than 1018. The hot rolled bars used in the manufacture of this product are of special quality. Most bars are cold drawn, although some larger sizes are turned and polished.

When higher degrees of dimensional accuracy and straightness are required, we recommend the use of PRECISION SHAFTING, which is produced by grinding and polishing. Refer to Pages 11 and 12 of this section.

ANALYSIS

	Carbon	Manganese	Phosphorus	Sulphur
1040	.37/.44	.60/.90	.04 Max.	.05 Max.
1042	.40/.47	.60/.90	.04 Max.	.05 Max.
1045	.43/.50	.60/.90	.04 Max	.05 Max.

APPLICATIONS — This material is used where greater strength is required than can be obtained from the lower carbon steels. It responds to heat treatment, and a wide range of properties can be obtained. Applications include shafts, machinery parts, bolts, pinions, gears, etc.

MECHANICAL PROPERTIES — The following values are average and may be considered as representative:

	Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
1" rd., cold drawn	110,000	85,000	19%	32%	223
5" rd., turned & polished	90,000	55,000	26%	50%	187

MACHINABILITY — Machinability rating is approximately 64% based on 1212 as 100%. Average surface cutting speed is between 95 and 105 feet per minute.

WELDABILITY — Due to higher carbon content, this material is not readily welded. With thin sections and flexible design, gas or arc welding may be used without preheating, but in joints over 1/2" to 3/4" thick preheating is necessary. To develop equivalent strength in a weld, a low alloy filler is recommended. Stress relieving after welding is also recommended. The grade of welding rod to be used depends thickness of section, design, service requirement, etc.

HARDENING — This steel is essentially water-hardening, but it may be quenched in oil. The recommended quenching temperatures are 1550°F for water and 1575°F for oil. A wide range of mechanical properties can be obtained by tempering at different temperatures between 700°F and 1300°F. Tempering in the range from 500°F to 700°F should be avoided.

1040/42/45 COLD FINISHED BARS (Continued)



1040/42/45 COLD FINISHED ROUNDS

Stock Lengths: 20' Approx.

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.					
	Per Foot	20-Ft. Bar		Per Foot	20-Ft. Bar		Per Foot	20-Ft. Bar				
1/4	.1671	3.341	1	1 11/16	7.612	152.2	3 3/8	30.45	608.9			
5/16	.2610	5.220		3/4	8.186	163.7	7/16	31.58	631.7			
3/8	.3759	7.517		13/16	8.781	175.6	1/2	32.74	654.8			
7/16	.5116	10.23		7/8	9.397	187.9	5/8	35.12	702.5			
1/2	.6682	13.36		15/16	10.03	200.7	3/4	37.59	751.7			
9/16	.8457	16.91		2	10.69	213.8	15/16	41.44	828.8			
5/8	1.044	20.88			1/16	11.37	227.4	4	42.77	855.3		
11/16	1.263	25.27			1/8	12.07	241.4		1/4	48.28	965.6	
3/4	1.504	30.07			3/16	12.79	255.8		3/8	51.16	1023	
13/16	1.765	35.29			1/4	13.53	270.6		7/16	52.63	1053	
7/8	2.046	40.93			5/16	14.29	285.9		1/2	54.13	1083	
15/16	2.349	46.98			3/8	15.08	301.5		5/8	57.18	1143	
I	2.673	53.46			7/16	15.88	317.6		3/4	60.31	1206	
	1/16	3.017			60.35	1/2	16.71		334.1	5	66.82	1336
	1/8	3.383			67.66	9/16	17.55		351.0		1/4	73.67
	3/16	3.769	75.38		5/8	18.42	368.4		7/16		79.03	1581
	1/4	4.176	83.53		11/16	19.31	386.1		1/2		80.86	1617
	5/16	4.604	92.09		3/4	20.21	404.3		3/4		88.37	1767
	3/8	5.053	101.1		7/8	22.09	441.9		6		96.22	1924
	7/16	5.523	110.5		15/16	23.06	461.3				1/4	104.4
	1/2	6.014	120.3	3	24.06	481.1	1/2				112.9	2259
	9/16	6.526	130.5		1/8	26.10	522.0	7			131.0	2619
	5/8	7.058	141.2		1/4	28.23	564.6					



1040/42/45 COLD DRAWN SQUARES

Stock Lengths: 12' Approx.

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.				
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar			
1/4	.2127	2.552	I	1 1/8	4.307	51.69		
5/16	.3323	3.988		3/16	4.799	57.59		
3/8	.4786	5.743		1/4	5.318	63.81		
1/2	.8508	10.21		1/2	7.657	91.89		
5/8	1.329	15.95		3/4	10.42	125.1		
3/4	1.914	22.97		2	13.61	163.4		
7/8	2.606	31.27			1/4	17.23	206.7	
I	3.403	40.84			1/2	21.27	255.2	
	I	3.403			40.84	3	30.63	367.5



1040/42/45 COLD DRAWN HEXAGONS

Stock Lengths: 12' Approx.

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.				
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar			
3/4	1.658	19.89	I	1 5/16	5.077	60.93		
7/8	2.257	27.08		3/8	5.572	66.87		
15/16	2.590	31.08		1/2	6.631	79.56		
I	2.947	35.37		3/4	9.026	108.3		
	1/8	3.730		44.76	7/8	10.36	124.3	
	3/16	4.156		49.87	2	11.79	141.5	
	1/4	4.605		55.26		1/2	18.42	221.0

1045 PRECISION SHAFTING

ASTM A 108 UNS G10450

Color Marking: Ends painted Olive

Precision Shafting represents the highest degree of over-all accuracy, concentricity, straightness, and surface perfection attainable in commercial practice. After being ground on centerless grinders, bars are polished to a high finish and carefully straightened.

The general RMS finish for 1045 Precision Shafting is 20 RMS maximum.

ANALYSIS

Carbon	Manganese	Phosphorus	Sulphur
.43/.50	.60/.90	.04 Max.	.05 Max.

APPLICATIONS — This product is often referred to as pump shafting or pump rod, due to its high degree of straightness, which is so important in high-speed shafting applications. This special straightness serves to prevent vibration and wear on packings and bearings, which must be avoided in deep well pump work. Precision Shafting is also used for motor shafts and similar applications where high-speed work necessitates straightness and accuracy along with the ability to be machined unsymmetrically with practically no danger of warpage.

TOLERANCE — 1½" & Under: Plus .000", Minus .001"
Over 1½" to Under 2½": Plus .000", Minus .0015"
2 ½" to 3" inclusive: Plus .000", Minus .002"
Over 3" to 4": Plus .000", Minus .003"
Over 4" to 6": Plus .000", Minus .006"

MECHANICAL PROPERTIES — The following are average and may be considered as representative:

	Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
1", cold drawn ground & polished	100,000	85,000	19%	32%	223
7", turned ground & polished	95,000	60,000	24%	48%	197

MACHINABILITY — Machinability rating is approximately 64% based on 1212 as 100%. Average surface cutting speed is 95 to 105 feet per minute.


WELDABILITY — Due to higher carbon content, this material is not readily welded. With thin sections and flexible design, gas or arc welding may be used without preheating, but in joints over ½" to ¾" thick preheating is necessary. To develop equivalent strength in a weld, a low alloy filler is recommended. Stress relieving after welding is also recommended. The grade of welding rod to be used depends on thickness of section, design, service requirements, etc.



1045 PRECISION SHAFTING

Stock Lengths 20' - 0¹/₄" and 21' - 24'

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	20' - 0 ¹ / ₄ " Bar		Per Foot	20' - 0 ¹ / ₄ " Bar
1/2	.6682	13.38	2 1/2	16.71	334.5
9/16	.8457	16.93	5/8	18.42	368.8
5/8	1.044	20.90	11/16	19.31	386.6
11/16	1.263	25.29	3/4	20.21	404.6
3/4	1.504	30.11	7/8	22.09	442.3
13/16	1.765	35.34	15/16	23.06	461.7
7/8	2.046	40.96	3	24.06	481.7
15/16	2.349	47.03	3/16	27.16	543.8
1	2.673	53.52	1/4	28.23	565.1
1/16	3.017	60.40	3/8	30.45	609.6
1/8	3.383	67.73	7/16	31.58	632.3
3/16	3.769	75.46	1/2	32.74	655.5
1/4	4.176	83.61	11/16	36.35	727.8
5/16	4.604	92.18	3/4	37.59	752.6
3/8	5.053	101.2	15/16	41.44	829.7
7/16	5.523	110.6	4	42.77	856.3
1/2	6.014	120.4	1/4	48.28	966.6
9/16	6.526	130.7	7/16	52.63	1054
5/8	7.058	141.3	1/2	54.13	1084
11/16	7.612	152.4	3/4	60.31	1207
3/4	8.186	163.9	15/16	65.16	1305
13/16	8.781	175.8	5	66.82	1338
7/8	9.397	188.1	1/4	73.67	1475
15/16	10.03	200.8	7/16	79.03	1582
2	10.69	214.0	1/2	80.86	1619
1/8	12.07	241.7	3/4	88.37	1769
3/16	12.79	256.1	15/16	94.23	1887
1/4	13.53	270.9	6	96.22	1926
3/8	15.08	301.9	1/2	112.9	2260
7/16	15.88	317.9	7	131.0	2623

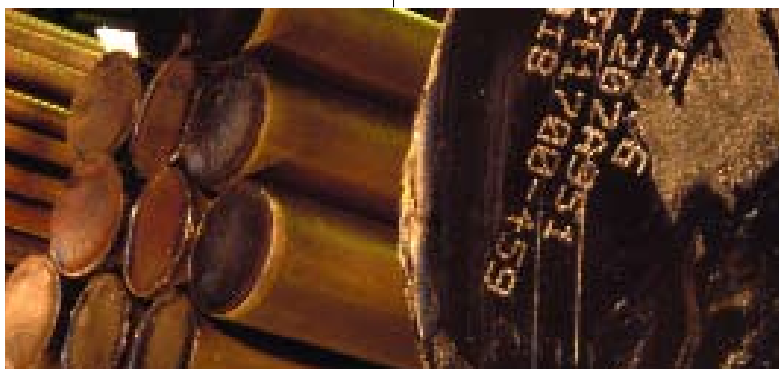

1213/15 FREE MACHINING COLD FINISHED BARS

(SCREW MACHINE STOCK)

ASTM A 108 UNS G12130

Color Marking: Ends painted Orange

1213 and 1215 are resulfurized and rephosphorized free machining steels, commonly referred to as Screw Stock. They are improved free-cutting steels that have replaced the Bessemer B-1113 grade. They are especially suited for automatic screw machine operations where the major requirement is exceptional free-cutting quality with a good finish.

ANALYSIS

	Carbon	Manganese	Phosphorus	Sulphur
1213	.13 Max.	.70/1.00	.07/.12	.24/.33
1215	.09 Max.	.75/1.05	.04/.09	.26/.35

APPLICATIONS — This Screw Stock was developed for manufacturing numerous parts requiring considerable machining, close finish tolerances, and a bright smooth finish. Beyond ordinary machining, it will respond to roll threading, nibbing, and some minor bending without cracking. It is not recommended for forming, ordinary bending, or upsetting, nor for parts subject to severe fatigue stresses.

MECHANICAL PROPERTIES — The following are average values for 1" round and may be considered as representative:

Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
87,500	75,000	15%	42%	187

MACHINABILITY — Machinability rating is 136%, based on 1212 as 100%. Average surface cutting speed is 225 feet per minute.

WELDABILITY — Due to their very high sulphur, these grades are not considered as weldable.

HARDENING — Although this analysis will respond to conventional treatments, it is not considered a case-hardening steel. Better results can be obtained from 1117 or 1018.



1213 — 1215 COLD DRAWN HEXAGONS

Stock Lengths 10' to 12'

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar	
1/8	.0461	.5526	13/16	1.946	23.35	1	1 11/16	8.393	100.7
5/32	.0720	.8635	7/8	2.257	27.08		3/4	9.026	108.3
3/16	.1036	1.243	15/16	2.590	31.08	13/16	9.682	116.2	
7/32	.1410	1.692	1	2.947	35.37	7/8	10.36	124.3	
1/4	.1842	2.210		1/16	3.327	39.93	2	11/79	141.5
5/16	.2878	3.454	1/8	3.730	44.76	1/8		13.31	159.7
11/32	.3483	4.179	3/16	4.156	49.87	3/16	14.10	169.2	
3/8	.4145	4.973	1/4	4.605	55.26	1/4	14.92	179.0	
7/15	.5641	6.769	5/16	5.077	60.93	3/8	16.62	199.5	
1/2	.7368	8.842	3/8	5.572	66.87	7/16	17.51	210.1	
9/16	.9325	11.19	7/16	6.090	73.08	1/2	18.42	221.0	
5/8	1.151	13.82	1/2	6.631	79.56	5/8	20.31	243.7	
11/16	1.393	16.72	9/16	7.196	86.35	3/4	22.29	267.5	
3/4	1.658	19.89	5/8	7.783	93.39	3	26.53	318.3	
							1/2	36.10	433.2


1213 — 1215 COLD FINISHED BARS (Continued)



**1213 — 1215 COLD DRAWN or
GROUND & POLISHED ROUNDS**

Stock Lengths: 12' Approx.

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	12 Ft. Bar		Per Foot	12 Ft. Bar
3/32	.0235	.2820	1 5/8	7.058	84.70
1/8	.0418	.5012	1 1/16	7.612	91.34
9/64	.0529	.6343	3/4	8.186	98.23
5/32	.0653	.7831	13/16	8.781	105.4
11/64	.0790	.9475	7/8	9.397	112.8
3/16	.0940	1.128	15/16	10.03	120.4
13/64	.1103	1.323	2	10.69	128.3
7/32	.1279	1.535	1/16	11.37	136.4
1/4	.1671	2.005	1/8	12.07	144.8
17/64	.1886	2.263	3/16	12.79	153.5
9/32	.2114	2.537	1/4	13.53	162.4
5/16	.2610	3.132	5/16	14.29	171.5
21/64	.2878	3.453	3/8	15.08	180.9
11/32	.3158	3.790	7/16	15.88	190.6
3/8	.3759	4.510	1/2	16.71	200.5
25/64	.4079	4.894	9/16	17.55	210.6
13/32	.4411	5.293	5/8	18.42	221.0
7/16	.5116	7.048	11/16	19.31	231.7
15/32	.5873	7.048	3/4	20.21	242.6
1/2	.6682	8.019	13/16	21.14	253.7
17/32	.7544	9.052	7/8	22.09	265.1
9/16	.8457	10.15	15/16	23.06	276.8
19/32	.9423	11.31	3	24.06	288.7
5/8	1.044	12.53	1/8	26.10	313.2
21/32	1.151	13.81	1/4	28.23	338.8
11/16	1.263	15.16	3/8	30.45	365.3
23/32	1.381	16.57	1/2	32.74	392.9
3/4	1.504	18.04	5/8	35.12	421.5
49/64	1.567	18.80	3/4	37.59	451.0
25/32	1.631	19.58	7/8	40.14	481.6
13/16	1.765	21.17	4	42.77	513.2
27/32	1.903	22.83	1/8	45.48	545.8
7/8	2.046	24.56	1/4	48.28	579.3
57/64	2.120	25.44	3/8	51.16	613.9
15/16	2.349	28.19	1/2	54.13	649.5
31/32	2.508	30.10	3/4	60.31	723.7
1	2.673	32.07	5	66.82	801.9
1/16	3.017	36.21	1/4	73.67	884.0
1/8	3.383	40.59	3/8	77.22	926.6
3/16	3.769	45.23	1/2	80.86	970.2
1/4	4.176	50.12	3/4	88.37	1060
5/16	4.604	55.25	6	96.22	1155
3/8	5.053	60.64	1/2	112.9	1355
7/16	5.523	66.28	7	131.0	1572
1/2	6.014	72.17	1/2	150.4	1805
9/16	6.526	78.31			



1213 — 1215 COLD DRAWN SQUARES

Stock Lengths 11' to 12'

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	12 Ft. Bar		Per Foot	12 Ft. Bar
1/8	.0531	.6381	1	3.403	40.84
3/16	.1196	1.436	1/8	4.307	51.69
1/4	.2127	2.552	1/4	5.318	63.81
5/16	.3323	3.988	3/8	6.434	77.21
3/8	.4786	5.743	1/2	7.657	91.89
7/16	.6514	7.817	5/8	8.987	107.8
1/2	.8508	10.21	3/4	10.42	125.1
9/16	1.077	12.92	2	13.61	163.4
5/8	1.329	15.95	1/8	15.37	184.4
11/16	1.609	19.30	3/8	19.20	230.4
3/4	1.914	22.97	1/2	21.27	255.2
7/8	2.606	31.27	3	30.63	367.5
15/16	2.991	35.89			

SUPER FREE MACHINING STEELS—LEADED

12L14

ASTM A 108 as applicable UNS G12144

Color Marking

12L14: Ends painted Brown and White

12L14Te: Ends painted Pink and Purple

These products represent the latest developments in the field of free machining carbon steels available.

ANALYSIS

	Carbon	Man- ganese	Phos- phorus	Sulphur	Lead	Other
12L14	.15 Max.	.85/1.15	.04/.09	.26/.35	.15/.35	—
12L14Te	.15 Max.	.85/1.15	.04/.09	.26/.35	.15/.35	Tellurium

APPLICATIONS — Used to maximum advantage for parts where considerable machining is required, such as bushings, inserts, couplings, and hydraulic hose fittings. With good ductility, these grades are suitable for parts involving bending, crimping, or riveting.

MECHANICAL PROPERTIES — The following are average and may be considered as representative:

Tensile Strength	Yield Strength	Elongation in 2"	Reduction of Area	Brinell Hardness
78,000 PSI	70,000 PSI	15%	50%	163 BHN

MACHINABILITY — Average surface cutting speeds and machinability ratings based on 1212 as 100% are as follows:

12L14	325 feet per minute—193%
12L14Te	420 feet per minute—250%

WELDABILITY — Due to high sulphur content, these grades are not considered as weldable.

HARDENING — Although these grades will respond to conventional treatments, they are not considered case-hardening steels. Better results can be obtained from 1117 or 1018.

For more complete data on these steels, ask for special literature.

SUPER FREE MACHINING - LEADED (Continued)



ROUNDS

Stock Lengths: 11' to 13'



HEXAGONS

Stock Lengths: 11' to 13'

Size			Est. Wt., Lbs.			Size			Est. Wt., Lbs.			Size			Est. Wt., Lbs.		
In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.
Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar
1/8	.0418	.5012	1 5/16	4.604	55.25	1/4	.1842	2.210	1 7/16	6.090	73.08						
9/64	.0529	.6548	3/8	5.053	60.64	5/16	.2878	3.454	1/2	6.631	79.56						
5/32	.0653	.7831	7/16	5.523	66.28	3/8	.4145	4.973	9/16	7.196	86.35						
3/16	.0940	1.128	1/2	6.014	72.17	7/16	.5641	6.769	5/8	7.783	93.39						
7/32	.1279	1.535	9/16	6.526	78.31	1/2	.7368	8.842	1 1/16	8.393	100.7						
1/4	.1671	2.005	5/8	7.058	84.70	9/16	.9325	11.19	3/4	9.026	108.3						
9/32	.2114	2.537	1 1/16	7.612	91.34	5/8	1.151	13.82	1 3/16	9.682	116.2						
19/64	.2356	2.827	3/4	8.186	98.23	1 1/16	1.393	16.72	7/8	10.36	124.3						
5/16	.2610	3.132	13/16	8.781	105.4	3/4	1.658	19.89	2	11.79	141.5						
21/64	.2877	3.452	7/8	9.397	112.8	1 3/16	1.946	23.35	1/4	14.92	179.0						
1 1/32	.3158	3.790	15/16	10.03	120.4	7/8	2.257	27.08	3/8	16.62	199.5						
3/8	.3759	4.510	2	10.69	128.3	15/16	2.590	31.08	1/2	18.42	221.0						
25/64	.4078	4.894	1/16	11.37	136.4	I	2.947	35.37	5/8	20.31	243.7						
13/32	.4411	5.293	1/8	12.07	144.8	1/16	3.327	39.93	3/4	22.29	267.5						
27/64	.4758	5.710	3/16	12.79	153.5	1/8	3.730	44.76	7/8	24.36	292.3						
7/16	.5116	6.139	1/4	13.53	162.4	3/16	4.156	49.87	3	26.53	318.3						
29/64	.5488	6.586	5/16	14.29	171.5	1/4	4.605	55.26	1/4	31.13	373.6						
15/32	.5873	7.048	3/8	15.08	180.9	5/16	5.077	60.93	1/2	36.10	433.2						
1/2	.6682	8.019	7/16	15.88	190.6	3/8	5.572	66.87	4	47.16	565.9						
33/64	.7106	8.527	1/2	16.71	200.5												
17/32	.7544	9.052	9/16	17.55	210.6												
35/64	.7994	9.593	5/8	18.42	221.0												
9/16	.8457	10.15	1 1/16	19.31	231.7												
37/64	.8934	10.72	3/4	20.21	242.6												
19/32	.9425	11.31	13/16	21.14	253.7												
5/8	1.044	12.53	7/8	22.09	265.1												
41/64	1.097	13.16	15/16	23.06	276.8												
21/32	1.151	13.81	3	24.06	288.7												
43/64	1.207	14.48	1/16	25.07	300.1												
11/16	1.263	15.16	1/8	26.10	313.2												
23/32	1.381	16.57	1/4	28.23	338.8												
47/64	1.442	17.30	3/8	30.45	365.3												
3/4	1.504	18.04	1/2	32.74	392.9												
49/64	1.567	18.80	9/16	33.92	407.0												
25/32	1.631	19.58	5/8	35.12	421.5												
13/16	1.765	21.17	3/4	37.59	451.0												
27/32	1.903	22.83	7/8	40.14	481.6												
7/8	2.046	24.56	4	42.77	513.2												
57/64	2.120	25.44	1/8	45.48	545.8												
29/32	2.195	26.34	1/4	48.28	579.3												
15/16	2.349	28.19	3/8	51.16	613.9												
31/32	2.508	30.10	1/2	54.13	649.5												
I	2.673	32.07	3/4	60.31	723.7												
1/64	2.757	33.08	7/8	63.52	762.3												
1/16	3.017	36.21	5	66.82	801.9												
1/8	3.383	40.59	1/4	73.76	884.0												
9/64	3.477	41.72	1/2	80.86	970.2												
3/16	3.769	45.23	3/4	88.37	1060												
1/4	4.176	50.12	6	96.22	1155												



SQUARES

Stock Lengths: 11' to 13'

Size			Est. Wt., Lbs.			Size			Est. Wt., Lbs.		
In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.	In	Per	12-Ft.
Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar	Inches	Foot	Bar
1/4	.2127	2.552	1 5/16	2.991	35.89						
5/16	.3323	3.988	I	3.403	40.84						
3/8	.4786	5.743	1/16	3.842	46.10						
7/16	.6514	7.817	1/8	4.307	51.69						
1/2	.8508	10.21	13/64	4.803	57.64						
9/16	1.077	12.92	1/4	5.318	63.81						
5/8	1.329	15.95	3/8	6.434	77.21						
1 1/16	1.609	19.30	1/2	7.657	91.89						
3/4	1.914	22.97	5/8	8.987	107.8						
13/16	2.247	26.96	3/4	10.42	125.1						
7/8	2.606	31.27	2	13.61	163.4						
			1/4	17.23	206.7						

1117 AND 11L17 (Leaded)
COLD FINISHED BARS
ASTM A 108 UNS G 11170

Color Marking

1117: Ends painted Aluminum with Red Stripe

11L17: Ends painted Aluminum with Orange Stripe

This grade is low-carbon high-manganese steel. It possesses much of the machining quality of 1212 Screw Stock but with improved mechanical properties. This grade also has excellent carburizing properties. Bars are produced from special quality hot rolled bars.

1117 is available as a leaded steel (11L17) in certain sizes. The addition of .15/.35 per cent lead improves free-machining characteristics without sacrificing carburizing properties.

ANALYSIS

Carbon	Manganese	Phosphorus	Sulphur
.14/.20	1.00/1.30	.04 Max.	.08/.13

APPLICATIONS — This steel is used in automatic screw machines for manufacturing numerous parts requiring considerable machining and close tolerances, along with a smooth finish. It may be bent or formed where such cold working operations are not too severe. It is especially suitable for carburized parts requiring soft core and high surface hardness, such as gears, pinions, worms, king pins, ratchets, dogs, etc.

MECHANICAL PROPERTIES — The following are average values for 1" cold drawn round and may be considered as representative of the grade:

Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
80,000	70,000	16%	50%	156

MACHINABILITY — 1117 has a machinability rating of 91%, based on 1212 as 100%. Average surface cutting speed is 150 feet per minute. 11L17 will machine at approximately 170 surface feet per minute.

WELDABILITY — This grade is not readily welded due to high sulphur content. Gas or arc welding may be used providing joints are preheated. To develop equivalent strength in a weld, a low alloy filler is recommended. Stress relieving after welding is also recommended. The grade of welding rod to be used depends on the thickness of section, design, service requirements, etc.

HARDENING — This grade will respond to any of the standard carburizing methods and subsequent heat treatments. For a hard case and a tough core, the following heat treatment is suggested: Carburize at 1650°-1700°F for approximately eight hours. Cool in box and reheat to 1400°-1450°F. Quench in water and draw at 300°-350°F.



1117 COLD DRAWN SQUARES

Stock Lengths: 12' Approx.

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	12 Ft. Bar		Per Foot	12 Ft. Bar
1	3.403	40.84	2 1/2	21.27	255.2
1/8	4.307	51.69	3	30.63	367.5
1/4	5.318	63.81	3 1/2	41.69	500.3
3/8	6.434	77.21	3/4	47.86	574.3
1/2	7.657	91.89	4 1/2	68.91	827.0
2	13.61	163.4	5	85.08	1021

1117 AND 11L17 (LEADED) COLD FINISHED BARS (Continued)



1117 AND 11L17 (Leaded) COLD FINISHED ROUNDS

Stock Lengths: 12' and 20', Approx.

Size In Inches	Estimated Weight, Lbs.			Size In Inches	Estimated Weight, Lbs.		
	Per Foot	12-Ft. Bar	20-Ft. Bar		Per Foot	12-Ft. Bar	20-Ft. Bar
1/8	.0418	.5012	—	2	10.69	128.3	213.8
3/16	.0940	1.128	—	1/16	11.37	136.4	227.4
7/32	.1279	1.535	—	1/8	12.07	144.8	241.4
1/4	.1671	2.005	—	3/16	12.79	153.5	255.8
9/32	.2114	2.537	—	1/4	13.53	162.4	270.6
5/16	.2610	3.132	—	5/16	14.29	171.5	285.9
11/32	.3158	3.790	—	3/8	15.08	180.9	301.5
3/8	.3759	4.510	—	7/16	15.88	190.6	317.6
13/32	.4411	5.293	—	1/2	16.71	200.5	334.1
7/16	.5116	6.139	—	9/16	17.55	210.6	351.0
15/32	.5873	7.048	—	5/8	18.42	221.0	368.4
1/2	.6682	8.019	—	11/16	19.31	213.7	386.1
17/32	.7544	9.052	—	3/4	20.21	242.6	404.3
9/16	.8457	10.15	—	13/16	21.14	253.7	422.9
5/8	1.044	12.53	—	7/8	22.09	265.1	441.9
21/32	1.151	13.81	23.02	15/16	23.06	276.8	461.3
11/16	1.263	15.16	25.27	3	24.06	288.7	481.1
3/4	1.504	18.04	30.07	1/8	26.10	313.2	522.0
13/16	1.765	21.17	35.29	1/4	28.23	338.8	564.6
7/8	2.046	24.56	40.93	3/8	30.45	365.3	608.9
15/16	2.349	28.19	46.98	1/2	32.74	392.9	654.8
31/32	2.508	30.10	50.17	5/8	35.12	421.5	702.5
1	2.673	32.07	53.46	3/4	37.59	451.0	751.7
1/64	2.757	33.08	55.14	7/8	40.14	481.6	802.7
1/16	3.017	36.21	60.35	4	42.77	513.2	855.3
1/8	3.383	40.59	67.66	1/8	45.48	545.8	909.6
3/16	3.769	45.23	75.38	1/4	48.28	579.3	965.6
1/4	4.176	50.12	83.53	3/8	51.16	613.9	1023
5/16	4.604	55.25	92.09	1/2	54.13	649.5	1083
3/8	5.053	60.64	101.1	3/4	60.31	723.7	1206
7/16	5.523	66.28	110.5	7/8	63.52	762.3	1270
1/2	6.014	72.17	120.3	5	66.82	801.9	1336
9/16	6.526	78.31	130.5	1/4	73.67	884.0	1473
5/8	7.058	84.70	141.2	1/2	80.86	970.2	1617
11/16	7.612	91.34	152.2	3/4	88.37	1060	1767
3/4	8.186	98.23	163.7	6	96.22	1155	1924
13/16	8.781	105.4	175.6				
7/8	9.397	112.8	187.9				
15/16	10.03	120.4	200.7				



1117 COLD DRAWN HEXAGONS

Stock Lengths 11' to 13'

Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.		Size In Inches	Est. Wt., Lbs.	
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar
1/4	.1842	2.210	1	2.947	35.37	2	11.79	141.5
5/16	.2878	3.454	1/16	3.327	39.93	1/8	13.31	159.7
3/8	.4145	4.973	1/8	3.730	44.76	1/4	14.92	179.0
7/16	.5641	6.769	3/16	4.156	49.87	3/8	16.62	199.5
1/2	.7368	8.842	1/4	4.605	55.26	7/16	17.51	210.1
9/16	.9325	11.19	5/16	5.077	60.93	1/2	18.42	221.0
5/8	1.151	13.82	3/8	5.572	66.87	5/8	20.31	243.7
11/16	1.393	16.72	7/16	6.090	73.08	3/4	22.29	267.5
3/4	1.658	19.89	1/2	6.631	79.56	3	26.53	318.3
13/16	1.946	23.35	5/8	7.783	93.39			
7/8	2.257	27.08	11/16	8.393	100.7			
15/16	2.590	31.08	3/4	9.026	108.3			
			13/16	9.682	116.2			
			7/8	10.36	124.3			

11L17 (LEADED) COLD FINISHED BARS (Continued)

11L17 (LEADED) COLD DRAWN FLATS



Stock Lengths 10' and 12'

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar
5/16 x	1	1.064	13/8 x	4 1/2	21.05
3/8 x	1 1/4	1.595		5 1/2	25.73
	1 1/2	1.914	1 1/2 x	1 3/4	8.933
	2	2.552		2	10.21
	2 1/2	3.191		2 1/2	12.76
	3	3.829		3	15.31
1/2 x	3 1/4	4.148		3 1/2	17.87
	3/4	1.276		4	20.42
	7/8	1.489		4 1/2	22.97
	1	1.702		5	25.52
	1 1/2	2.552		6	30.63
	1 3/4	2.978		6 1/2	33.18
	2	3.403		7	35.73
	2 1/2	4.254		8 1/2	43.39
5/8 x	1	2.127		1 5/8 x	2 1/2
	1 1/2	3.191			3
	2	4.254			3 1/2
	3	6.381		1 3/4 x	2 1/2
	3 1/2	7.445			3
	3 3/4	7.976			3 1/2
	4 1/2	9.572			3 3/4
3/4 x	5 1/2	11.70			4
	1 1/4	3.191			4 1/2
	1 1/2	3.829			5
	2	5.105			5 1/2
	2 1/2	6.381			6 1/2
	3	7.657			6 3/4
	4 1/2	11.49			7
	5	12.76			7 1/2
	6	15.31			8
	6 1/2	16.59			8 1/2
7/8 x	5	14.89			9
	6 1/2	19.36			9 1/2
1 x	1 1/4	4.254			10
	1 1/2	5.105			10 1/2
	1 5/8	5.530			11
	1 3/4	5.956			11 1/2
	2	6.806			12
	2 1/4	7.657			12 1/2
	2 1/2	8.508			13
	2 3/4	9.359			13 1/2
	3	10.21			14
	4	13.61			14 1/2
	4 1/2	15.31			15
	7 1/2	25.52			15 1/2
	8 1/2	28.93			16
1 1/8 x	2	7.657			16 1/2
	2 1/2	9.572			17
	3	11.49			17 1/2
1 1/4 x	1 3/8	5.264			18
	1 1/2	6.381			18 1/2
	1 3/4	7.445			19
	2 1/2	10.64			19 1/2
	3 3/4	15.95			20
	4	17.02			20 1/2
	4	19.14			21
	5	21.27			21 1/2
	5 1/2	23.40			22
					22 1/2
					23
					23 1/2
					24
					24 1/2
					25
					25 1/2
					26
					26 1/2
					27
					27 1/2
					28
					28 1/2
					29
					29 1/2
					30
					30 1/2
					31
					31 1/2
					32
					32 1/2
					33
					33 1/2
					34
					34 1/2
					35
					35 1/2
					36
					36 1/2
					37
					37 1/2
					38
					38 1/2
					39
					39 1/2
					40
					40 1/2
					41
					41 1/2
					42
					42 1/2
					43
					43 1/2
					44
					44 1/2
					45
					45 1/2
					46
					46 1/2
					47
					47 1/2
					48
					48 1/2
					49
					49 1/2
					50
					50 1/2
					51
					51 1/2
					52
					52 1/2
					53
					53 1/2
					54
					54 1/2
					55
					55 1/2
					56
					56 1/2
					57
					57 1/2
					58
					58 1/2
					59
					59 1/2
					60
					60 1/2
					61
					61 1/2
					62
					62 1/2
					63
					63 1/2
					64
					64 1/2
					65
					65 1/2
					66
					66 1/2
					67
					67 1/2
					68
					68 1/2
					69
					69 1/2
					70
					70 1/2
					71
					71 1/2
					72
					72 1/2
					73
					73 1/2
					74
					74 1/2
					75
					75 1/2
					76
					76 1/2
					77
					77 1/2
					78
					78 1/2
					79
					79 1/2
					80
					80 1/2
					81
					81 1/2
					82
					82 1/2
					83
					83 1/2
					84
					84 1/2
					85
					85 1/2
					86
					86 1/2
					87
					87 1/2
					88
					88 1/2
					89
					89 1/2
					90
					90 1/2
					91
					91 1/2
					92
					92 1/2
					93
					93 1/2
					94
					94 1/2
					95
					95 1/2
					96
					96 1/2
					97
					97 1/2
					98
					98 1/2
					99
					99 1/2
					100

1137 AND 1141 COLD FINISHED BARS

ASTM A 108 UNS G 11370 UNS G 11410

Color Marking

1137: Ends Painted Gold

1141: Ends Painted Purple

These grades are medium-carbon steels processing higher mechanical properties than other medium carbon steels, as well as free machining properties.

ANALYSIS

	Carbon	Manganese	Phosphorus	Sulphur
1137	.32/.39	1.35/1.65	.04 Max.	.08/.13
1141	.37/.45	1.35/1.65	.04 Max.	.08/.13

APPLICATIONS — These grades, because of their free machining properties, are usually processed in automatic screw machines. They are recommended for studs, axles, pins, bolts, and various machinery parts requiring considerable machining, close finish tolerances, bright finish, and high mechanical properties.

MECHANICAL PROPERTIES— The following values are average for 1" round, and may be considered as representative of these grades:

	Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
1137	95,000	85,000	11%	30%	187
1141	100,000	90,000	10%	30%	197

MACHINABILITY— 1137 has a machinability rating of 72%, based on 1212 as 100%. Average surface cutting speed is 120 feet per minute. 1141 has a machinability rating of 70%, based on 1212 as 100%. Average surface cutting speed is 115 feet per minute.

WELDABILITY — These grades are not readily welded due to the higher carbon and sulphur content. Gas of arc welding may be used providing joints are preheated. To develop equivalent strength in a weld, a low alloy filler is recommended. Stress relieving after welding is also recommended. The grade of welding rod to be used depends on the thickness of section, design, service requirements, etc.

HARDENING — Although primarily oil hardening steels, these grades can be water quenched, but great care should be exercised when this is done. The quenching temperature is 1500°-1600°F, with the temperature being 25°F lower for water quench. Temper to required hardness.

1137 AND 1141 COLD FINISHED BARS (Continued)



1137 AND 1141 COLD FINISHED ROUNDS

Stock Lengths: 12' Approx.

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar
3/16	.0940	1.128	1 11/16	7.612	91.34
1/4	.1671	2.005	3/4	8.186	98.23
5/16	.2610	3.132	13/16	8.781	105.4
3/8	.3759	4.510	7/8	9.397	112.8
7/16	.5116	6.139	15/16	10.03	120.4
1/2	.6682	8.019	2	10.69	128.3
9/16	.8457	10.15	1/16	11.37	136.4
5/8	1.044	12.53	1/8	12.07	144.8
41/64	1.097	13.16	3/16	12.79	153.5
21/32	1.151	13.81	1/4	13.53	162.4
11/16	1.263	15.16	5/16	14.29	171.5
3/4	1.504	18.04	3/8	15.08	180.9
49/64	1.567	18.80	7/16	15.88	190.6
25/32	1.631	19.58	1/2	16.71	200.5
13/16	1.765	21.17	5/8	18.42	221.0
7/8	2.046	24.56	3/4	20.21	242.6
29/32	2.195	26.34	7/8	22.09	265.1
15/16	2.349	28.19	3	24.06	288.7
31/32	2.508	30.10	1/8	26.10	313.2
1	2.673	32.07	3/16	27.16	325.9
1/16	3.017	36.21	1/4	28.23	338.8
1/8	3.383	40.59	3/8	30.45	365.3
3/16	3.769	45.23	1/2	32.74	392.9
1/4	4.176	50.12	5/8	35.12	421.5
5/16	4.604	55.25	3/4	37.59	451.0
3/8	5.053	60.64	4	42.77	513.2
7/16	5.523	66.28	1/4	48.28	579.3
1/2	6.014	72.17	1/2	54.13	649.5
9/16	6.526	78.31	3/4	60.31	723.7
5/8	7.058	84.70	5	66.82	801.9
			1/2	80.86	970.2

**STRESSPROOF® AND 1144 HI STRESS
COLD FINISHED BARS
ASTM A 311 Class B UNS G11440**

Color Marking: Ends painted Gray

These are carbon-manganese free machining grades which have been severely cold worked to produce high tensile properties. The bars are specially treated to relieve the stresses set up by the cold working, thus minimizing the tendency toward warpage after machining which is common in ordinary cold-drawn bars.

These steels have built-in high strength hardness, and wearability, without the necessity of heat treatment. Thus they are often used for parts requiring mechanical properties ordinarily obtained by heat treating an alloy grade to the Rockwell C hardness range of 23-30 after machining.

Both grades are available as Cold Drawn Bars or Ground and Polished Bars. The latter possess the close tolerances and fine finish normally found in ground and polished bars, plus the combination of free machinability, minimum warpage, high strength, and wearability not found in ordinary steels.

ANALYSIS

	Carbon	Manganese	Phosphorus	Sulphur
STRESSPROOF®	.40/.48	1.35/1.65	.040 Max.	.24/.33
1144 Hi Stress	.40/.48	1.35/1.65	.040 Max.	.24/.33

APPLICATIONS — Arbors, keyed shafts, spindles, gears, pinions, piston rods, sleeves, lead screws, racks, motor shafts, splined shafts, link pins, mandrels, boring bars, collets, bushings, drive-shafts, armature shafts, rotary pump shafts, gusher pump shafts, king pins, oil and water pump shafts, wrist pins, etc.

MECHANICAL PROPERTIES — The following are minimum properties per ASTM A311 Class B:

	Yield Strength (psi)	Tensile Strength (psi)	Elongation in 2"	Reduction of Area	Typical Rockwell "C" Hardness
Thru 2"	100,000	115,000	8%	25%	26
Over 2" thru 3"	100,000	115,000	8%	20%	25
Over 3"	100,000	115,000	7%	20%	24

MACHINABILITY — Machinability ratings are based on 1212 as 100%.

STRESSPROOF® — 83%, cutting speed 140 surface feet per minute.

1144 Hi Stress — 79%, cutting speed 130 surface feet per minute.

WELDABILITY — Welding of these grades is not recommended.

For more complete data on this steel, ask for special literature.



**STRESSPROOF® and 1144 HI STRESS HEXAGONS
Cold Drawn**

Stock Lengths: 20' Approx.

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.		
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar	
3/8	.4145	4.973	1	2.947	35.37	
7/16	.5641	6.769		1/16	3.327	39.93
1/2	.7368	8.842		1/8	3.730	44.76
9/16	.9325	11.19		1/4	4.605	55.26
5/8	1.151	13.82		3/8	5.572	66.87
11/16	1.393	16.72		1/2	6.631	79.56
3/4	1.658	19.89		5/8	7.783	93.39
13/16	1.946	23.35		3/4	9.026	108.3
7/8	2.257	27.08		2	11.79	141.5
15/16	2.590	31.08				

STRESSPROOF® and 1144 STRESS COLD FINISHED BARS (Continued)



STRESSPROOF® AND 1144 HI STRESS ROUNDS

Cold Drawn Stock Lengths: 12' Approx.						Ground & Polished Stock Lengths: 20' Approx.					
Size		Est. Wt., Lbs.		Size		Est. Wt., Lbs.		Size		Est. Wt., Lbs.	
In	Per Foot	12-Ft. Bar	In	Per Foot	12-Ft. Bar	In	Per Foot	20-Ft. Bar	In	Per Foot	20-Ft. Bar
7/32	.1280	1.540	1 3/4	8.186	98.23	5/16	.2610	5.220	1 11/16	7.612	152.2
1/4	.1671	2.005	1 3/16	8.781	105.4						
17/64	.1886	2.263	7/8	9.397	112.8	3/8	.3759	7.517	3/4	8.186	163.7
9/32	.2114	2.537	15/16	10.03	120.4						
5/16	.2610	3.132	2	10.69	128.3	7/16	.5116	10.23	7/8	9.397	187.9
21/64	.2878	3.453	1/16	11.37	136.4						
3/8	.3759	4.510	1/8	12.07	144.8	1/2	.6682	13.36	15/16	10.03	207.2
25/64	.4078	4.894	3/16	12.79	153.5	9/16	.8457	16.91	2	10.69	213.8
27/64	.4758	5.710	1/4	13.53	162.4						
7/16	.5116	6.139	5/16	14.29	171.5	5/8	1.044	20.88	1/8	12.07	241.4
1/2	.6682	8.019	3/8	15.08	180.9						
33/64	.7106	8.527	7/16	15.88	190.6	11/16	1.263	25.27	3/16	12.79	255.8
17/32	.7544	9.052	1/2	16.71	200.5						
9/16	.8457	10.15	9/16	17.55	210.6	3/4	1.504	30.07	1/4	13.53	270.6
5/8	1.044	12.53	5/8	18.42	221.0						
41/64	1.097	13.16	11/16	19.31	231.7	13/16	1.765	35.29	3/8	15.08	301.5
11/16	1.263	15.16	3/4	20.21	242.6						
3/4	1.504	18.04	13/16	21.14	253.7	7/8	2.046	40.93	7/16	15.88	317.6
49/64	1.567	18.80	7/8	22.09	265.1						
13/16	1.765	21.17	15/16	23.06	276.8	15/16	2.349	46.98	1/2	16.71	334.1
7/8	2.046	24.56	3	24.06	288.7	1	2.673	53.46	5/8	18.42	368.4
57/64	2.120	25.44	1/16	25.07	300.8						
15/16	2.349	28.19	1/8	26.10	313.2	13/16	1.765	35.29	3/4	20.21	404.3
1	2.673	32.07	1/4	28.23	338.8	1/16	3.017	60.35	15/16	23.06	461.2
1/64	2.757	33.08	5/16	29.33	351.9	1/8	3.383	67.66			
1/16	3.017	36.21	3/8	30.45	365.3						
1/8	3.383	40.59	7/16	31.58	379.0	3/16	3.769	75.38	3	24.06	481.1
5/32	3.573	42.88	1/2	32.74	392.9						
3/16	3.769	45.23	5/8	35.12	421.5	1/4	4.176	83.53	1/4	28.23	564.6
1/4	4.176	50.12	3/4	37.59	451.0						
5/16	4.604	55.25	7/8	40.14	481.6	5/16	4.604	92.09	1/2	32.74	654.8
11/32	4.826	57.91	15/16	41.44	497.3						
3/8	5.053	60.64	4	42.77	513.2	3/8	5.053	101.1	15/16	41.44	828.8
7/16	5.523	66.28	1/8	45.48	545.8	7/16	5.523	110.5	4	42.77	855.3
1/2	6.014	72.17	1/4	48.28	579.3						
9/16	6.526	78.31	3/8	51.16	613.9	1/2	6.014	120.3	1/4	48.28	965.6
5/8	7.058	84.70	1/2	54.13	649.5	5/8	7.058	141.2	1/2	54.13	1083
11/16	7.612	91.34									

FATIGUE-PROOF®
COLD FINISHED BARS
ASTM A 108 UNS G11440

Color Marking: Ends painted Red and White

FATIGUE-PROOF® is a medium-carbon free-machining steel with higher mechanical properties than its companion product, STRESSPROOF®. These properties are produced by a process of drawing steel at elevated temperatures, developed and patented by LaSalle Steel Co. The result is a steel with high tensile strength, uniformity of properties, and excellent machinability.

This product possesses high strength as it is received from the mill, and no subsequent heat treatment is required. The strength is remarkably uniform from the surface to the center of the bar and from end to end. Properties are not adversely affected by exposure to temperatures up to 600°F. Where higher hardness is required, material may be selectively hardened by induction heating. Water quenching will produce Rockwell "C" 60, and oil quenching will yield Rockwell "C" 50-55.

FATIGUE-PROOF® has excellent machinability for a material of its strength. In standard practice, it will machine up to 25% faster than annealed alloy steels and up to 75% faster than heat-treated alloy steels. Excellent dimensional stability is maintained. Tool use as well as surface finish is better.

ANALYSIS

Carbon	Manganese	Phosphorus	Sulphur	Silicon
.40/.48	1.35/1.65	.040 Max.	.24/.33	.15/.35

APPLICATIONS — Shafts, spindles, gears, arbors, pinions, lead screws, wrist pins, milling machine spindles, splined power take-off shafts, pump shafts, etc.

MECHANICAL PROPERTIES—FATIGUE-PROOF® possesses the minimum tensile, yield, and hardness values shown below. Other properties shown are typical of the grade.

Tensile Strength (psi)	Yield Strength (psi)	Elongation in 2"	Reduction of Area	Brinell Hardness
140,000	125,000	5-15%	15-30%	280

MACHINABILITY—FATIGUE-PROOF® machines approximately 80% as fast as 1212. Average surface cutting speed is 134 feet per minute.

WELDABILITY — Welding of this grade is not recommended. However, it can be welded using a coated low hydrogen rod. Amperage and penetration must be kept low.



FATIGUE-PROOF® ROUNDS
Cold Drawn
Stock Lengths 12'

Size In Inches	Estimated Weight, Lbs.		Size In Inches	Estimated Weight, Lbs.	
	Per Foot	12-Ft. Bar		Per Foot	12-Ft. Bar
1/4	.1671	2.005	1 5/16	4.604	55.25
5/16	.2610	3.132	3/8	5.053	60.64
3/8	.3759	4.510	7/16	5.523	66.28
7/16	.5120	6.144	1/2	6.014	72.17
1/2	.6682	8.019	9/16	6.526	78.31
9/16	.8457	10.15	5/8	7.058	84.70
5/8	1.044	12.53	11/16	7.612	91.34
21/32	1.151	13.81	3/4	8.186	98.23
11/16	1.263	15.16	13/16	8.781	105.4
3/4	1.504	18.04	7/8	9.397	112.8
13/16	1.765	21.17	15/16	10.03	120.4
7/8	2.046	24.56	2	10.69	128.3
15/16	2.349	28.19	1/8	12.07	144.8
1	2.673	32.07	3/16	12.79	153.5
1/16	3.017	36.21	1/4	13.53	162.4
1/8	3.383	40.59	3/8	15.08	180.9
3/16	3.769	45.23	1/2	16.71	200.5
1/4	4.176	50.12	5/8	18.42	221.0

CHROME PLATED CARBON STEEL BARS
C1045, C1050, 1045 MICROALLOY
ASTM B117 Salt Spray Tested
UNS G10450, G10500

This material is intended for use primarily as cylinder piston rods.

ANALYSIS

	C	Mn	P	S	Si	V
C1045	.43/.50	.60/.90	.04 Max	.05 Max		
C1050	.45/.55	.70/1.00	.04 Max	.05 Max		
1045 Microalloy.44		.80	.014	.27	.31	.105

MECHANICAL PROPERTIES (Typical)

C1045 Microalloy	100 ksi Tensile, 75 ksi Yield, 20% Elongation
C1045 Hot Rolled	60 ksi Tensile, 50 ksi Yield, 26% Elongation
C1045/C1050 Cold Drawn	113 ksi Tensile, 100 ksi Yield, 20% Elongation
C1045/C1050 Cold Drawn Induction Hardened	115 ksi Tensile, 100 ksi Yield, 20% Elongation

Chrome Thickness: .0005" Minimum except 1 1/2"
from each end not plated.

Chrome Hardness: HRC 68-72

Surface Finish: 16 RMS Max.

Induction Hardened Case Depth: .050" Minimum except 1 1/2"
from each end is not hardened.

Induction Hardened Surface: HRC 50 Minimum

SIZES AND WEIGHTS — Round

OD	Wt/Ft	50	75	100	100 IH
0.313	.0262		x	x	
0.375	.0376		x	x	
0.500	0.668		x	x	x
0.625	1.044		x	x	x
0.750	1.504		x	x	x
0.875	2.046		x	x	
1.000	2.673		x	x	x
1.250	4.176		x	x	x
1.375	5.053		x	x	x
1.500	6.014		x	x	x
1.625	7.058		x	x	x
1.750	8.186		x	x	x
1.875	9.397		x	x	x
2.000	10.692		x	x	x
2.250	13.532		x	x	x
2.500	16.706		x	x	x
2.750	20.214		x	x	x
3.000	24.056		x	x	x
3.250	28.233		x	x	x
3.500	32.743		x	x	x
3.750	37.588		x	x	x
4.000	42.766		x	x	x
4.250	48.279		x	x	
4.500	54.126	x			
4.750	60.307	x			
5.000	66.823	x			
5.500	80.855	x			
6.000	96.224	x			
7.000	130.972	x			

1050 CARBON BAR FOR TIE-ROD APPLICATION

ASTM A 108 UNS G10500

1050 heavy draft cold drawn bar has a modified stress relief anneal to provide a 100 ksi minimum yield. Material is used where greater strength is required.

BRITISH STANDARD SPECIFICATIONS — 060 A 47, 080 M 46

APPLICATIONS — Primary used is for tie-rods for high pressure hydraulic cylinders.

SIZE RANGE — .236" - 1.250" (6mm - 32mm). Sizes are produced under nominal size to allow roll threading up to standard nut sizes.

TYPICAL CHEMICAL ANALYSIS

Carbon	Manganese	Phosphorus	Sulphur
.48/.55	.70/.100	.04 Max	.05 Max

TYPICAL MECHANICAL PROPERTIES

Tensile Strength (psi)	Yield Point (psi)	Elongation (in 2")
115,000	100,000 min.	19% -26%

AVERAGE CUTTING SPEED — 95-105 ft./min.

WELDABILITY — Not readily welded due to higher carbon content.

HARDENING — This steel is essentially water-hardening but may be quenched in oil.

HEAT TREATING — Responds to heat treatment. A wide range of properties can be obtained.

SIZES AND WEIGHTS — Round

Size(in.)	Lb/ft.
.225/.222	.1353
.284/.21	.2155
.346/.343	.3199
.466/.463	.5804
.587/.584	.9209
.706/.703	1.3322
.827/.824	1.8280
.951/.948	2.4173
1.069/1.065	3.0544
1.194/1.190	3.8105

Note: For all cold finished carbon bars, mechanical properties are not generally reported on our test reports.

For all your metal needs...
Call EMJ First! (800) 3EMJ-EMJ

© Copyright 2007
Earle M. Jorgensen Company